


ELEVATION

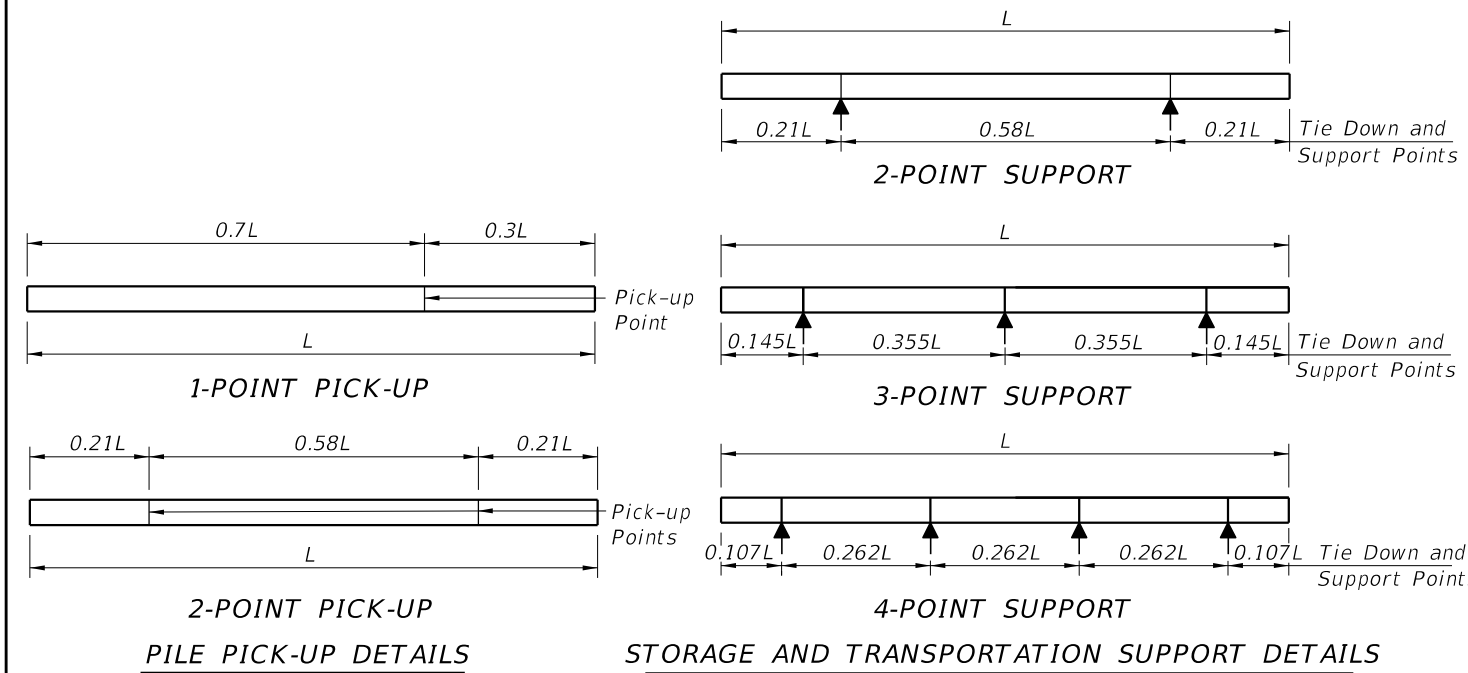

NOTES

1. Work this Index with the Pile Data Table in the Structures Plans.
2. Concrete:
  - A. Piles: Class V (Special)
  - B. Splice: Class IV
  - C. Silica Fume: See "GENERAL NOTES" in Structures Plans for locations where the use of silica fume, metakaolin or ultra-fine flyash is required for options using stainless steel strand and reinforcing.
3. Concrete Strength at time of prestress transfer:
  - A. Piles: 6,000 psi minimum.
4. Reinforcing:
  - A. Bars:
    - a. Stainless Steel: Meet the requirements of Specification Section 931 for Type 304, Grade 75.
    - b. Carbon FRP: Meet the requirements of Specification Section 932.
  - B. Prestressing Strands:
    - a. Stainless Steel: Seven-wire HSSS, UNS S32205 (Type 2205) or UNS S31803 strand, meeting the requirements of Specification Section 933.
    - b. Carbon FRP: Meet the requirements of Specification Section 933.
  - C. Spiral Ties:
    - a. One half turn is required for carbon steel spiral splice.
    - b. One full turn is required at the pile head and tip.
5. Pile Splices:
  - A. Epoxy: Type AB Epoxy Compound or Mortar must meet the requirements of Specification Section 926.
    - a. Use a Type AB Epoxy Bonding Compound or Epoxy Mortar, as recommended by the Manufacturer, to form the joint between pile sections.
    - b. Use a Type AB Epoxy Bonding Compound as a bonding agent on internal pile surfaces.
  - B. Driving: Resume pile driving after splice concrete reaches a minimum strength of 5,500 psi.
6. Mark piles at the pick-up points to indicate the proper points for attaching handling lines.

TABLE OF MAXIMUM PILE PICK-UP AND SUPPORT LENGTHS


Maximum Pile Length (Feet)	Required Storage and Transportation Detail	Pick-Up Detail
119	2, 3, or 4 point	1 Point
170	2, 3, or 4 point	2 Point

10/26/2016 9:23:39 AM


10/26/2016 9:23:42 AM

Spliced Precast/Post-Tensioned Pile Section

Driven Precast/Post-Tensioned Pile

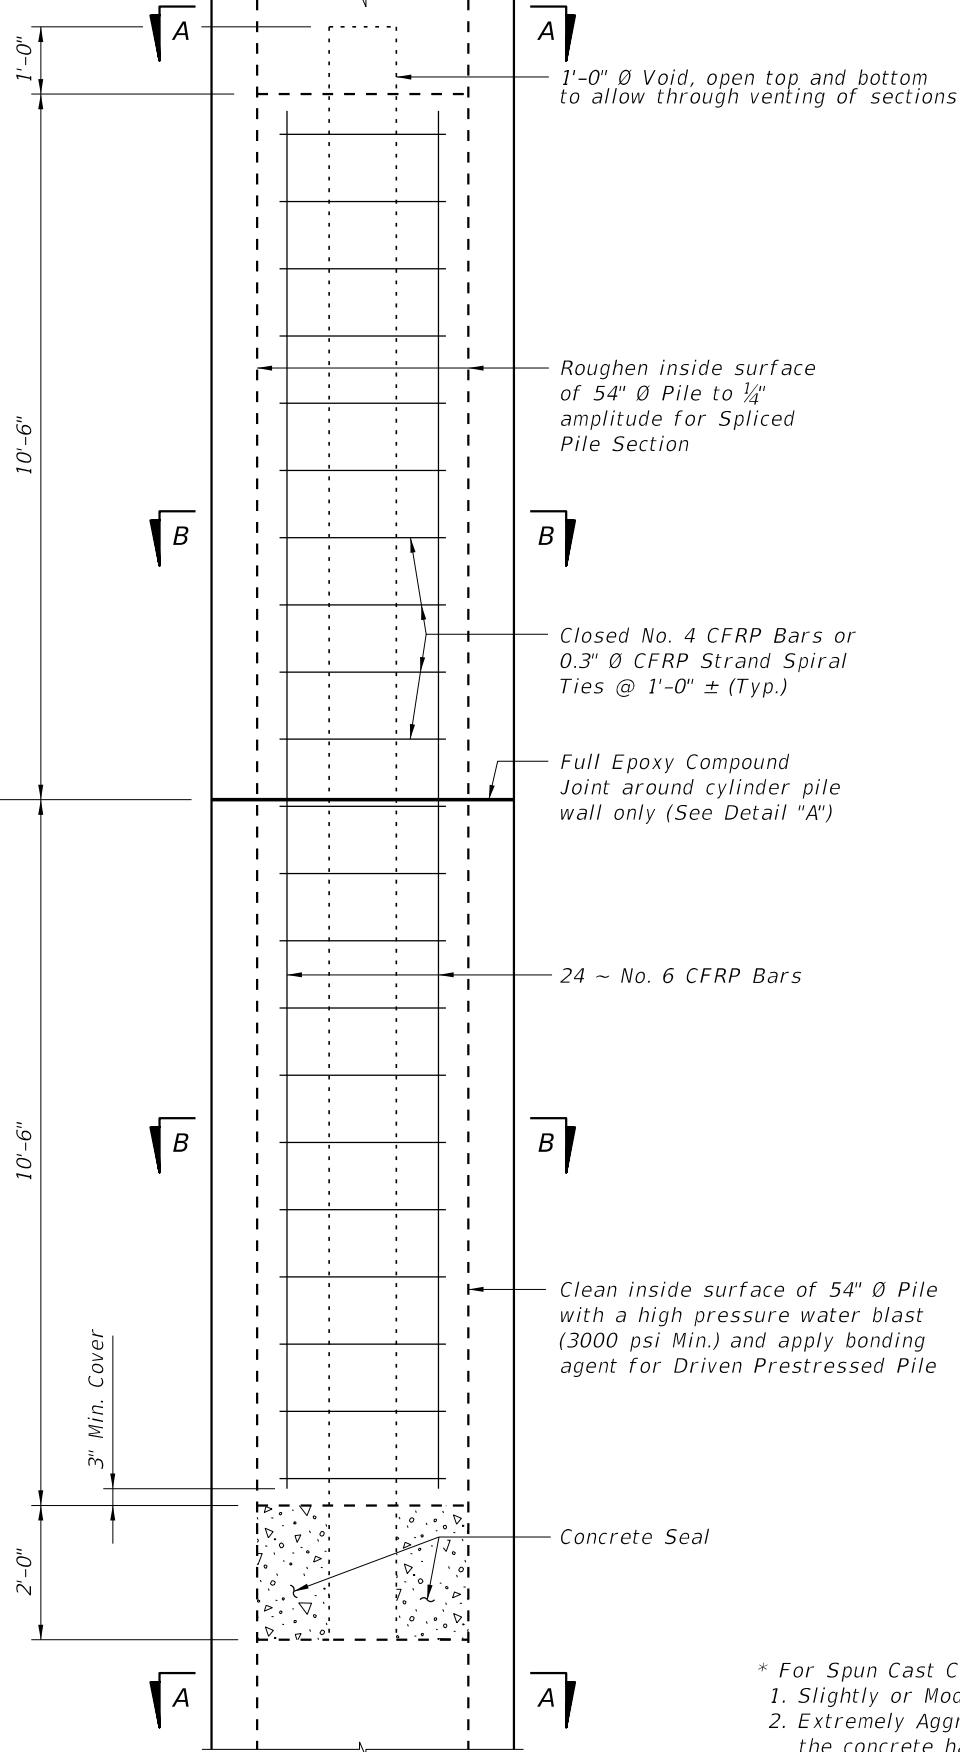


**DRIVABLE UNFORESEEN FIELD SPLICE DETAIL (Cast-In-Place Plug)**

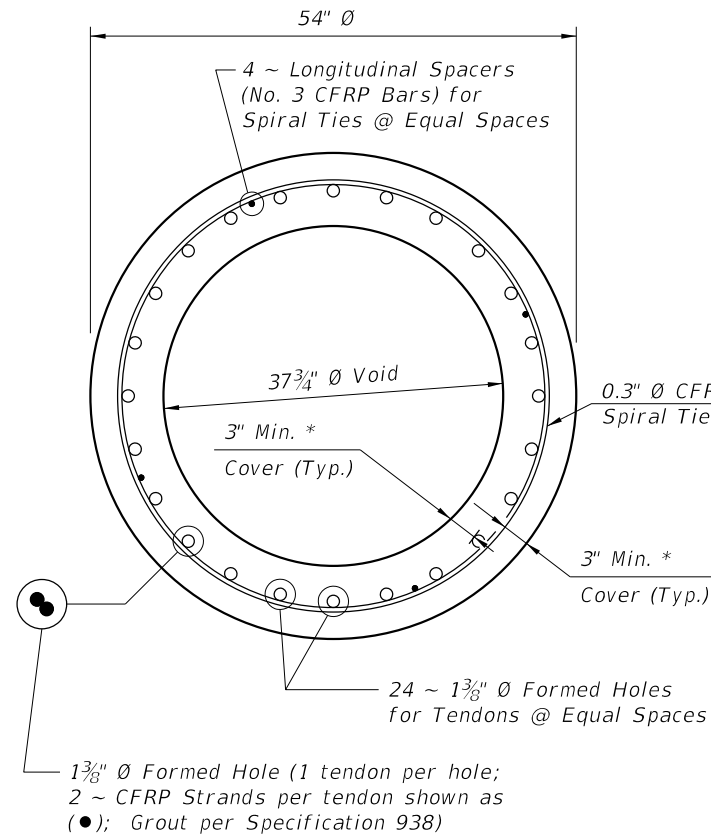


**SECTION A-A**

**ALTERNATE STRAND PATTERNS**

- 48 ~ 0.5"  $\emptyset$ , Single-Strand, at 28 kips
- 48 ~ 0.6"  $\emptyset$ , 7-Strand, at 29 kips

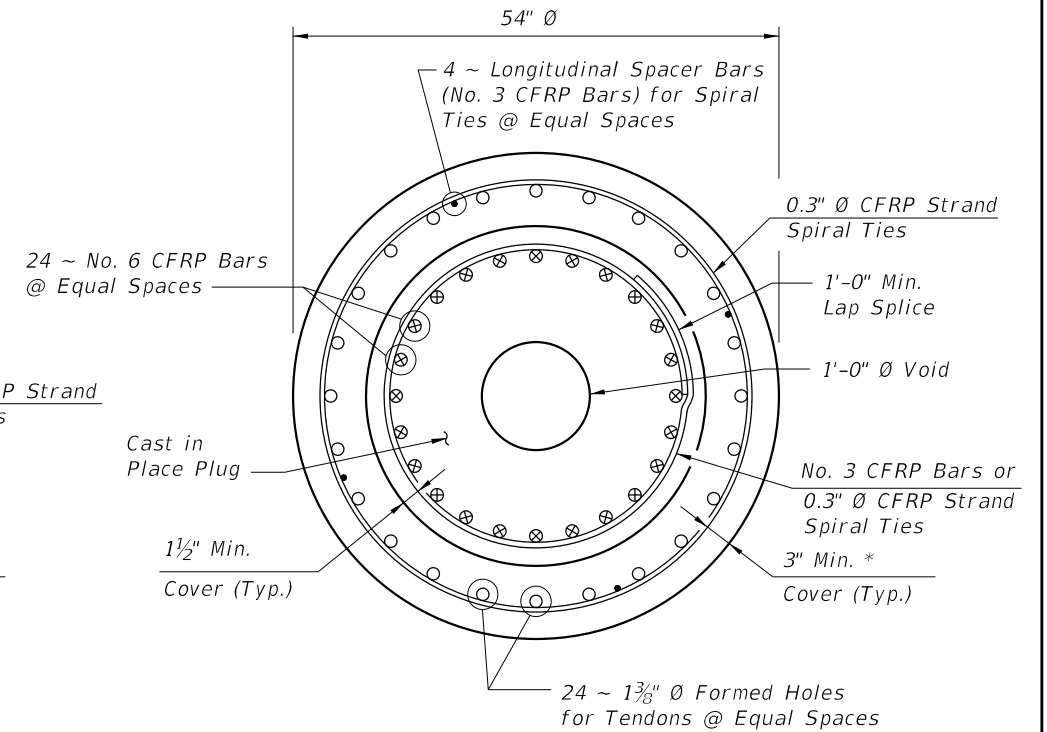

**SECTION B-B**

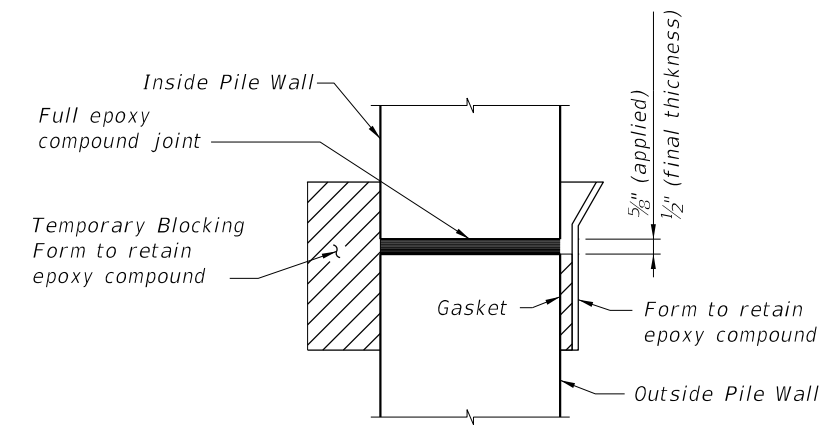

**DETAIL "A"**

\* For Spun Cast Cylinder Piles, the following requirements for concrete cover apply:  
 1. Slightly or Moderately Aggressive Environments: The concrete cover may be reduced to 2 inches.  
 2. Extremely Aggressive Environments: The concrete cover may be reduced to 2 inches as long as the concrete has a documented chloride ion penetration apparent diffusion coefficient with a mean value of 0.005 in<sup>2</sup> per year or less; otherwise, a 3-inch concrete cover is required.


**CFRP POST-TENSIONED PILE DETAILS**

LAST REVISION 01/01/16	DESCRIPTION:	FY 2017-18 DESIGN STANDARDS	54" PRECAST/POST-TENSIONED CFRP & SS CONCRETE CYLINDER PILE	INDEX NO. 22654	SHEET NO. 2 of 3
---------------------------	--------------	--------------------------------	--	--------------------	---------------------


10/26/2016 9:23:45 AM

Spliced Precast/Post-Tensioned Pile Section


Driven Precast/Post-Tensioned Pile

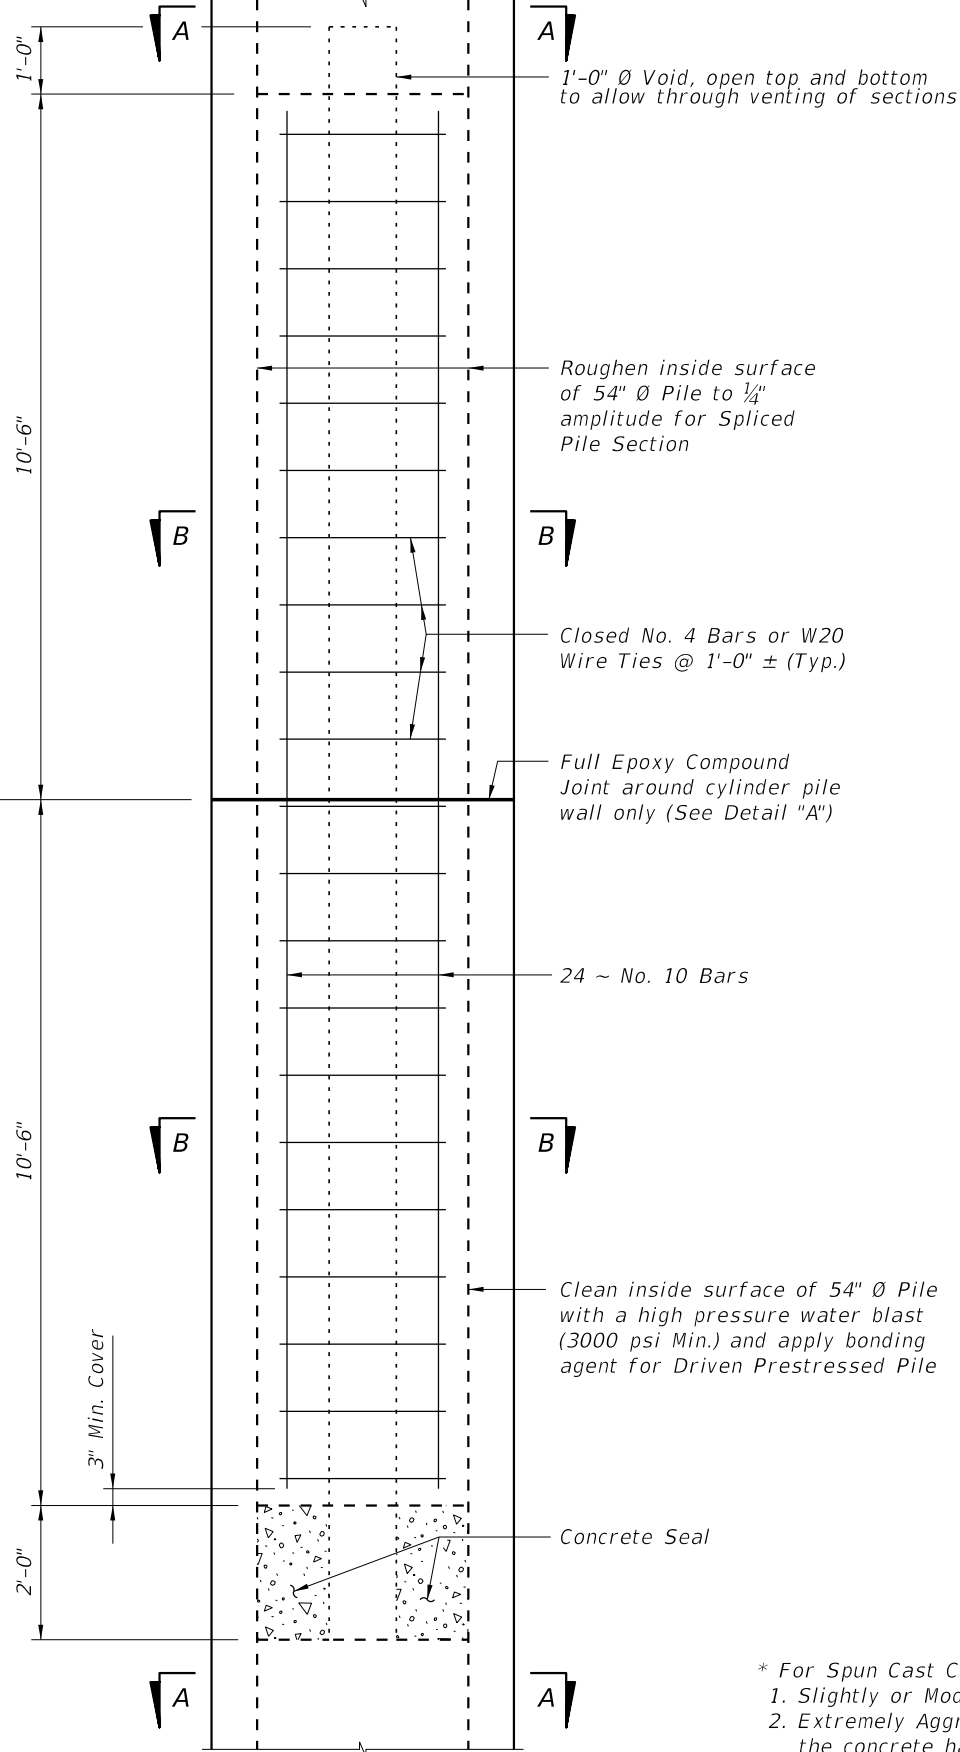

**DRIVABLE UNFORESEEN FIELD SPLICE DETAIL**  
(Cast-In-Place Plug)

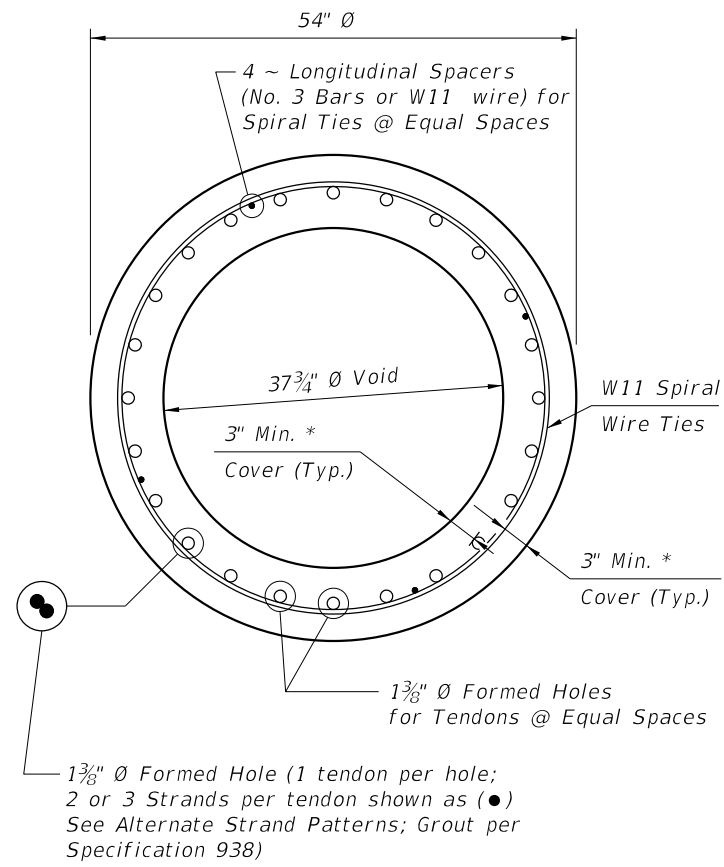

**SECTION A-A**

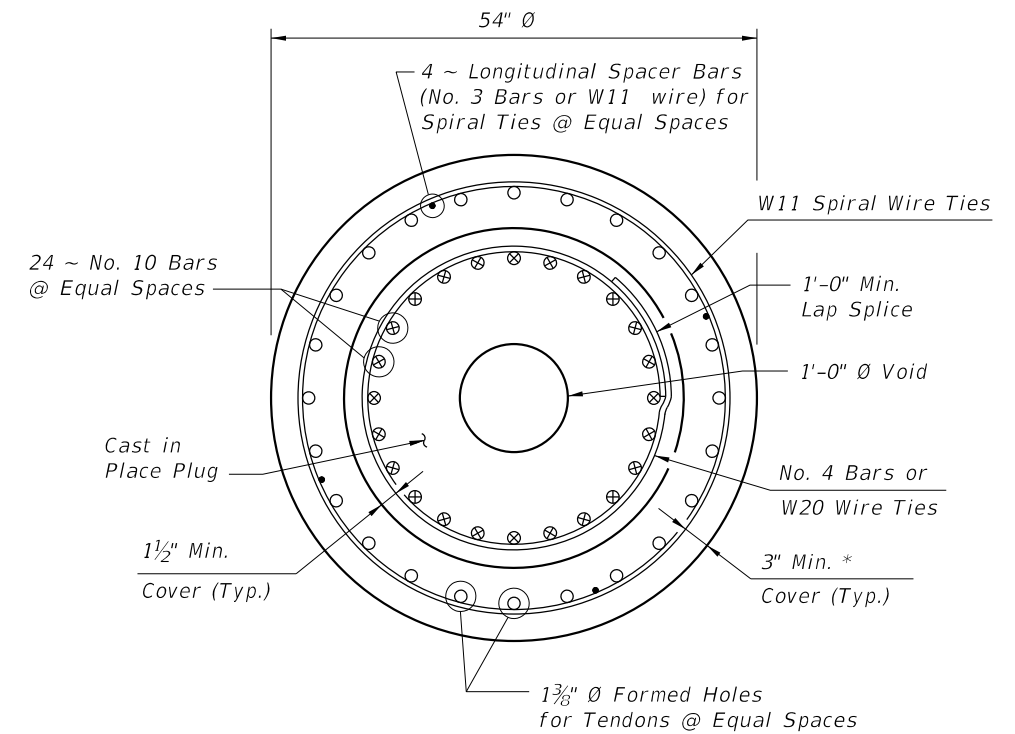


**SECTION B-B**

**ALTERNATE STRAND PATTERNS**

- 72 ~ 1/2" Ø, HSSS Strands, at 21 kips (24~3 strand tendons)
- 58 ~ 1/2" Ø, HSSS Strands, at 24 kips (29~2 strand tendons)
- 48 ~ 0.6" Ø, HSSS Strands, at 32 kips (24~2 strand tendons)

\* For Spun Cast Cylinder Piles, the following requirements for concrete cover apply:  
 1. Slightly or Moderately Aggressive Environments: The concrete cover may be reduced to 2 inches.  
 2. Extremely Aggressive Environments: The concrete cover may be reduced to 2 inches as long as the concrete has a documented chloride ion penetration apparent diffusion coefficient with a mean value of 0.005 in<sup>2</sup> per year or less; otherwise, a 3-inch concrete cover is required.

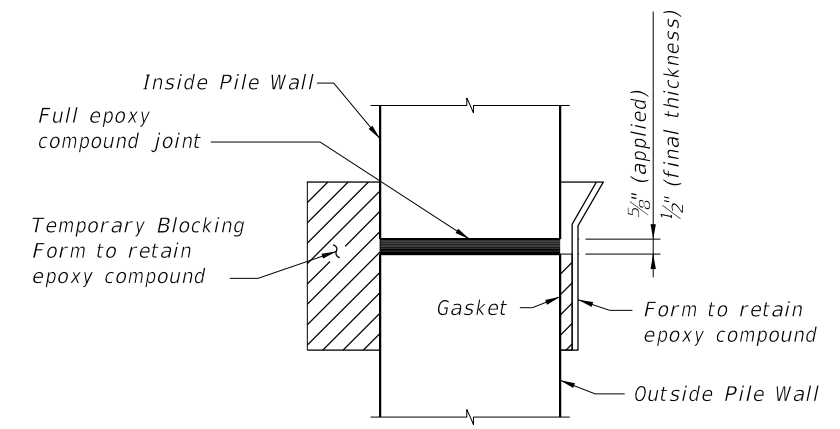

**DETAIL "A"**

**SS POST-TENSIONED PILE DETAILS**

LAST REVISION 01/01/16	DESCRIPTION:	<p>FY 2017-18 DESIGN STANDARDS</p>	<p>54" PRECAST/POST-TENSIONED CFRP &amp; SS CONCRETE CYLINDER PILE</p>	<p>INDEX NO. 22654</p>	<p>SHEET NO. 3 of 3</p>
---------------------------	--------------	--	--	----------------------------	-----------------------------